arXiv:1210.0911v1 [cond-mat.str-el] 2 Oct 2012

Magnetism of Fe and Ni from rotationally invariant Hirsch-Fye quantum Monte Carlo calculations

A. S. Belozerov,[1, 2] I. Leonov,[3] and V. I. Anisimov[1, 2]

[1] *Institute of Metal Physics, Russian Academy of Sciences, 620990 Yekaterinburg, Russia*
[2] *Ural Federal University, 620990 Yekaterinburg, Russia*
[3] *Theoretical Physics III, Center for Electronic Correlations and Magnetism, Institute of Physics, University of Augsburg, 86135 Augsburg, Germany*

(Dated: October 4, 2012)

We present a computational scheme for the investigation of complex materials with correlated electrons which allows one to take into account the spin rotational symmetry of the exchange Coulomb interaction. It combines *ab initio* band structure methods with dynamical mean-field theory and is implemented with the Hirsch-Fye quantum Monte Carlo algorithm in which the spin rotational invariance of Hund's exchange is restored by averaging over all possible directions of spin quantization axis. We employ this technique to perform benchmark calculations for the three-band Hubbard model on the infinite-dimensional Bethe lattice. Our results agree quantitatively well with those obtained using the continuous-time quantum Monte Carlo method. The proposed approach is employed to compute the electronic and magnetic properties of paramagnetic α iron and nickel. The obtained Curie temperatures agree well with experiment. Our results indicate that the magnetic transition temperature is significantly overestimated by using the density-density type of Coulomb interaction.

PACS numbers: 71.15.Mb, 71.20.Be, 71.27.+a

I. INTRODUCTION

The theoretical description of the electronic properties of transition metal compounds with partially filled d and f-shells and strong Coulomb interaction between the electrons remains a challenging, fundamental problem in condensed matter physics.[1,2] The interplay between electronic and lattice degrees of freedom in such materials results in their diverse physical properties and rich phase diagrams making these compounds particularly attractive for technological applications.[3] Moreover, orbital degeneracy is an important and often inevitable cause of this complexity. Together with the Hund's exchange interaction, it has important implications for the electronic and magnetic properties of correlated materials, leading to formation of local moments and complicated multiplet structures.

The electronic properties of correlated materials can be understood by employing the so-called LDA+DMFT approach,[1,4] a combination of *ab initio* local density approximation (LDA) of the density functional theory and dynamical mean-field theory (DMFT). Nowadays, the LDA+DMFT technique has become a state-of-the-art method for realistic description of correlated electron materials from first principles. This approach provides a systematic many-body treatment of the effect of local electronic correlations by taking into account temporal fluctuations while spatial fluctuations are neglected. Applications of LDA+DMFT for correlated electron compounds such as transition metals and their oxides have provided important insights into our understanding of the electronic and magnetic properties of these materials. In particular, by employing the LDA+DMFT technique it has become possible to obtain a good quantitative description of localized as well as delocalized electron states. In addition, the approach allows one to determine the electronic and magnetic properties of correlated compounds in both paramagnetic and magnetically ordered states.

Nevertheless, there are two important limitations of conventional implementations of the LDA+DMFT method. The first originates from the single-site (local) nature of DMFT. In particular, the key assumption of the theory is the limit of infinite spatial dimension, which allows one to perform an exact mapping of a complex lattice model (such as the Hubbard model) to a quantum impurity with an energy-dependent external bath, resulting in k-independent self-energy. However, in some cases the non-local spatial correlations can be essential to provide correct description of the properties of correlated materials.[5] For instance, the standard LDA+DMFT calculations are not able to capture the reduction of magnetic transition temperature due to long-wavelength spin waves. To resolve this problem there have been recently proposed several methods,[6] which we leave beyond the scope of our paper.

Since correlated materials often have several bands at the Fermi level, it requires specific treatment of the local Coulomb interaction, which in a cubic environment consists of the intra- and interorbital Coulomb interactions U and U', Hund's exchange J, and the pair-hopping coupling J'. These interactions obey spin and orbital rotational symmetry, thereby $U = U' + J + J'$ ensures the rotational invariance in the orbital space and $J = J'$ can be assumed whenever the spin-orbital coupling is negligible. Unfortunately, it is difficult to handle all these multiband interactions including Hund's exchange coupling and the pair hopping term with the quantum Monte

Carlo (QMC) method. In particular, a straightforward implementation leads to a severe sign problem making such simulations unfeasible. Therefore, at present, the most material-specific calculations employ the approximate form of the Coulomb repulsion restricted to the Ising-type exchange interaction. These calculations often provide a good quantitative description of the electronic, magnetic, and structural properties of correlated materials as a function of the reduced temperature T/T_{m}, where T_{m} is the calculated temperature of magnetic ordering.[7,8] However, the correct symmetry of the exchange interaction turns out to be essential for quantitative description of the electronic and magnetic properties of correlated systems.[9–13]

This problem can be overcome by using some quantum impurity solvers such as numerical renormalization group (NRG),[14] exact diagonalization (ED),[15] continuous-time quantum Monte Carlo (CT-QMC),[16] and others,[11,13] which allow one to treat the Coulomb interaction in its general form with preserved spin rotational symmetry. These calculations performed for the two- and three-band Hubbard models on the infinite-dimensional Bethe[10,12] and hypercubic[11] lattices show substantial overestimation of the magnetic transition temperature for the approximate Ising-type form of the exchange Coulomb interaction with respect to the rotationally invariant one. In accord with this, recent LDA+DMFT calculations of correlated compounds also indicate that the magnetic transition temperatures appear to be significantly overestimated by using the density-density type of Coulomb interaction.[7,13,17] However, applications of these techniques so far have been mostly limited to simple model systems and only a few realistic calculations for the $3d$ compounds have been recently presented.[18] This is mostly because of high computational costs (exponential with the number of orbitals) of these methods implemented with the full rotationally invariant Coulomb interaction which makes such calculations for the $3d$ and $4f$ materials extremely expensive. Obviously, the LDA+DMFT investigations of correlated materials with the Coulomb interaction in its general form with preserved spin rotational symmetry remain problematic and pose a great theoretical challenge.

In this paper, we present a novel implementation of the LDA+DMFT approach which allows us to take into account rotational symmetry of the exchange Coulomb interaction. This approach is formulated in terms of the Hirsch-Fye quantum Monte Carlo algorithm[19] where the spin rotational invariance of Hund's exchange is restored by averaging over all possible directions of spin quantization axis. It provides a robust and computationally efficient method which allows us to simulate the five-orbital systems at high temperatures. Using this technique we perform benchmark calculations for the three-band Hubbard model on the infinite-dimensional Bethe lattice. In addition, we employ the proposed approach to calculate the electronic and magnetic properties of paramagnetic α iron and nickel. To outline the importance of rotational symmetry of the exchange Coulomb interaction we compare our results with those obtained by using the density-density approximation.

This paper is organized as follows. In Sec. II we present a detailed formulation of the proposed approach which allows one to treat rotational invariance of the exchange interaction. In Sec. III we employ this technique to compute the electronic and magnetic properties of the three-band model on the Bethe lattice, paramagnetic α iron, and nickel. The obtained results are compared with those of previous calculations and experimental data. Finally, conclusions are presented in Sec. IV.

II. METHOD

The multiband Hamiltonian with full rotationally invariant on-site Coulomb interaction[20] can be written in the following form

$$\begin{aligned}\hat{H} &= U\sum_{m}\hat{n}_{m\uparrow}\hat{n}_{m\downarrow} \\ &+ \frac{1}{2}\sum_{\substack{mm'\sigma \\ m\neq m'}}\{(U-2J)\hat{n}_{m\sigma}\hat{n}_{m'\overline{\sigma}} + (U-3J)\hat{n}_{m\sigma}\hat{n}_{m'\sigma} \\ &- J(\hat{c}^{\dagger}_{m\sigma}\hat{c}_{m\overline{\sigma}}\hat{c}^{\dagger}_{m'\overline{\sigma}}\hat{c}_{m'\sigma} + \hat{c}^{\dagger}_{m\sigma}\hat{c}^{\dagger}_{m\overline{\sigma}}\hat{c}_{m'\sigma}\hat{c}_{m'\overline{\sigma}})\},\end{aligned} \tag{1}$$

where $\hat{c}^{+}_{m\sigma}$ ($\hat{c}_{m\sigma}$) denotes the creation (annihilation) operator of an electron with spin σ ($=\uparrow,\downarrow$) at orbital m, $\hat{n}_{m\sigma} = \hat{c}^{+}_{m\sigma}\hat{c}_{m\sigma}$, U is the screened Coulomb interaction parameter, J is the Hund's exchange coupling. The first three terms in Hamiltonian (1) correspond to the density-density part of Coulomb interaction and contain the exchange interaction in the Ising-type form. The remaining part consists of spin-flip (4th) and pair hopping (5th) terms. Using the z-projection of the spin operator, $\hat{S}^{z}_{m} = (\hat{n}_{m\uparrow} - \hat{n}_{m\downarrow})/2$, and the orbital occupancy operator, $\hat{N}_{m} = \hat{n}_{m\uparrow} + \hat{n}_{m\downarrow}$, the density-density part can be rewritten as

$$\begin{aligned}\hat{H}_{\mathrm{dd}} &= U\sum_{m}\hat{n}_{m\uparrow}\hat{n}_{m\downarrow} \\ &+ \frac{1}{2}\sum_{\substack{mm' \\ m\neq m'}}\{\bar{U}\hat{N}_{m}\hat{N}_{m'} - 2J\hat{S}^{z}_{m}\hat{S}^{z}_{m'}\},\end{aligned} \tag{2}$$

where $\bar{U} = U - 5J/2$ is the average value of the Coulomb interaction. The spin-flip term in Eq. (1) can be expressed via operators $\hat{S}^{x}_{m} = (\hat{c}^{\dagger}_{m\uparrow}\hat{c}_{m\downarrow} + \hat{c}^{\dagger}_{m\downarrow}\hat{c}_{m\uparrow})/2$ and $\hat{S}^{y}_{m} = -i(\hat{c}^{\dagger}_{m\uparrow}\hat{c}_{m\downarrow} - \hat{c}^{\dagger}_{m\downarrow}\hat{c}_{m\uparrow})/2$ as

$$\sum_{\sigma}\hat{c}^{\dagger}_{m\sigma}\hat{c}_{m\overline{\sigma}}\hat{c}^{\dagger}_{m'\overline{\sigma}}\hat{c}_{m'\sigma} = 2(\hat{S}^{x}_{m}\hat{S}^{x}_{m'} + \hat{S}^{y}_{m}\hat{S}^{y}_{m'}). \tag{3}$$

The pair hopping term acts only on high energy states with two electrons on the same orbital and thereby can be neglected. However, taking into account the spin-flip term in Eq. (1) is crucial for the correct description of spin dynamics. Therefore, the Coulomb interaction Hamiltonian can be written as

$$\hat{H} = U\sum_{m}\hat{n}_{m\uparrow}\hat{n}_{m\downarrow} + \frac{1}{2}\sum_{\substack{mm\prime \\ m\neq m'}}\{\bar{U}\hat{N}_m\hat{N}_{m'} - 2J\hat{\vec{S}}_m\hat{\vec{S}}_{m'}\}. \tag{4}$$

The Hamiltonian (4) with exchange term taken as a vector product, $J\hat{\vec{S}}_m\hat{\vec{S}}_{m'}$, is invariant with respect to the spin quantization axis rotations while the density-density counterpart with the Ising-type exchange term, $J\hat{S}^z_m\hat{S}^z_{m'}$, is not.

To restore the spin rotational symmetry of Hamiltonian (2) we here employ the method originally proposed by Hubbard.[21] The Coulomb interaction in Ref. 21 was considered in the following form

$$U\hat{N}_{\uparrow}\hat{N}_{\downarrow} = \frac{1}{4}U\hat{N}^2 - U\hat{S}_z^2 = \frac{1}{4}U\hat{N}^2 - U(\vec{e}\hat{\vec{S}})^2, \tag{5}$$

where $\hat{N}_\sigma = \sum_m \hat{n}_{m\sigma}$, $\hat{N} = \hat{N}_\uparrow + \hat{N}_\downarrow$, $\hat{S}_z = \sum_m \hat{S}^z_m$, $\vec{S}$ is the total spin of atom, $\vec{e}$ is an arbitrary unit vector that can be interpreted as a quantization axis. In order to restore the spin rotational symmetry in Eq. (5), averaging over all directions of $\vec{e}$ was introduced.

In this paper, we propose to restore the spin rotational invariance in Eq. (2) by averaging in the partition function calculation over all possible directions of spin quantization axis determined by the angles ϕ and θ:

$$Z \propto \int d\theta d\phi\, \mathrm{Tr}[e^{-\beta(\hat{H}_0 + U^\dagger(\theta,\phi)\hat{H}_{\mathrm{dd}}U(\theta,\phi))}]. \tag{6}$$

Here, $\hat{H}_0$ is a non-interacting part of impurity Hamiltonian, $U_{\sigma\sigma'}(\theta,\phi)$ stands for a transformation matrix for spin variables and reads as

$$U(\theta,\phi) = \begin{pmatrix} \cos(\theta/2)e^{i\phi/2} & \sin(\theta/2)e^{-i\phi/2} \\ -\sin(\theta/2)e^{i\phi/2} & \cos(\theta/2)e^{-i\phi/2} \end{pmatrix}. \tag{7}$$

According to Eq. 6, result does not depend on the choice of quantization axis direction and hence is rotationally invariant.

In the Hirsch-Fye quantum Monte Carlo algorithm,[19] dynamical potential matrix $V_{m\sigma}(\tau)$ is diagonal in spin and orbital indices and can be expressed as

$$V_\mu = \sum_{\nu(\neq\mu)}\lambda_{\mu\nu}s_{\mu\nu}\sigma_{\mu\nu}, \tag{8}$$

$$\sigma_{\mu\nu} = \begin{cases} 1, & \mu < \nu \\ -1, & \mu > \nu \end{cases},$$

where μ and ν are combined spin-orbital indices, $s_{\mu\nu}$ is an Ising-like variable taking the values ± 1, $\lambda_{\mu\nu} = \mathrm{arcosh}(e^{\Delta\tau U_{\mu\nu}/2})$. To average over all possible directions of spin quantization axis in the partition function (Eq. 6), one should consider the following potential

$$V'(\tau) = U^\dagger(\theta,\phi)V(\tau)U(\theta,\phi), \tag{9}$$

which is non-diagonal in spin index. Therefore, in QMC simulation Markov's chain should be defined not only by stochastic change of fluctuating fields but also by the stochastic change of angles θ and ϕ, corresponding to the quantization axis direction.

The physical meaning of the proposed rotationally invariant algorithm can be expressed as averaging over all possible directions of fluctuating spin polarization in the $3d$ shell, in contrast to polarization along the z-axis only in density-density Hamiltonian (2). Thereby this technique allows one to take into account not only the longitudinal spin fluctuations but also the transverse ones, reproducing the full spin dynamics.

III. RESULTS AND DISCUSSION

In this section, as a proof of concept we first present results of our model calculations in comparison with previous studies. In particular, we employ the proposed approach to compute the three-band Hubbard model on the infinite-dimensional Bethe lattice. We benchmark these calculations with the previously published results of the CT-QMC computations.[10] To study the role of symmetry of the exchange interaction we compare our results with those obtained by employing the density-density approximate form of the local Coulomb interaction.

To proceed further, we investigate the electronic and magnetic properties of paramagnetic iron and nickel. We outline importance of the correct spin and orbital rotational symmetry of the exchange interaction on the magnetic properties of these materials. To compute the magnetic properties of correlated materials we evaluate uniform magnetic susceptibility $\chi(T) = dM(T)/dH_z$ by measuring the induced magnetization in a small external magnetic field. Here, $M(T) = \sum_m(n_{m\uparrow} - n_{m\downarrow})$ is the magnetization induced by the external magnetic field H_z applied along the z axis (these calculations include the polarization of the impurity Weiss field due to the external magnetic field H_z). In our calculations, we adopted a few magnetic fields in the range from 0.01 to 0.04 eV to ensure linearity of response.

The calculated inverse uniform magnetic susceptibility exhibits a linear behavior at high temperatures which indicates the presence of local magnetic moments. The temperature dependence of $\chi(T)$ obeys the Curie-Weiss law $\chi(T) = C/(T - T_{\mathrm{C}})$, where C is a material-specific constant and T_{C} is the Curie temperature. The result of the least-square fit to the Curie-Weiss law is shown by the straight line. Therefore, the Curie temperature can be determined as an intersection of this line with the temperature axis.

A. Three-band model

In recent years the properties of the two- and three-orbital Hubbard models have been extensively investigated by using dynamical mean-field approach.[9–11,22] Here we would like to refer to Ref. 10 where the three-orbital Hubbard model on the infinite-dimensional Bethe lattice was studied by means of the continuous-time quantum Monte Carlo method with full rotationally invariant Coulomb interaction. In particular, it was established that the effect of spin-flip interactions considerably depends on a band filling. It was shown that the Mott-Hubbard physics dominates due to the strong effective Coulomb interaction U in the particle-hole symmetric case, while away from half-filling formation of local magnetic moments is more plausible due to the Hund's exchange. For the benchmark purposes we here reproduce these calculations by using the rotationally invariant HF-QMC method. We have chosen the same set of parameters as in Ref. 10. Namely, we consider the three-band model with two-electron occupancy. We adopt $U = 8t$ and $J = 1.2t$ for the Coulomb interaction and Hund's exchange, where t is a half of the non-interacting bandwidth. In Fig. 1 we present our results for the inverse uniform magnetic susceptibility. The calculated Curie temperatures are $0.29t$ and $0.15t$ for the conventional HF-QMC and rotationally invariant methods, respectively. These findings are in good quantitative agreement with results of the CT-QMC calculations, which give $T_C \sim 0.27t$ and $0.14t$ for the density-density and full rotationally invariant exchange, respectively. This quantitative agreement clearly demonstrates the validity of our method for accurate description of the spin dynamics. We note that transverse spin fluctuations can be regarded as an important source of softening of magnetic response. It is expected that in the five-band case this effect should be even more profound.

B. α iron

Elemental iron is one of the oldest and experimentally best studied itinerant ferromagnets. Various properties of iron can be understood on the basis of band-structure calculations.[23] In particular, these calculations provide a good description of the low-temperature ferromagnetic phase of Fe. However, applications of conventional band-structure techniques to describe the properties of paramagnetic iron, in particular, close to the $\alpha - \gamma$ phase transition, do not lead to satisfactory results. This is mainly due to the presence of local magnetic moments above the Curie temperature which are important for quantitative description of paramagnetic state. In this respect, the LDA+DMFT approach provides the best formalism which allows one to unify the localized and itinerant electron behavior in metallic magnets.

Applications of LDA+DMFT have shown to provide a good quantitative description of the electronic, magnetic, and structural properties of iron.[7,8,24–28] However, an agreement was achieved only in terms of the reduced temperature T/T_C, while the calculated Curie temperature T_C was found to be almost twice larger than the experimental value of 1043 K (Ref. 29). Recently the properties of iron have been investigated by means of $\vec{J}$-QMC method, which uses the static approximation for the charge degrees of freedom and treats the exchange Coulomb interaction in the rotationally invariant form.[13] These calculations indicate that substantial part of the Curie temperature overestimation comes from the approximate (density-density) treatment of the exchange Coulomb interaction.

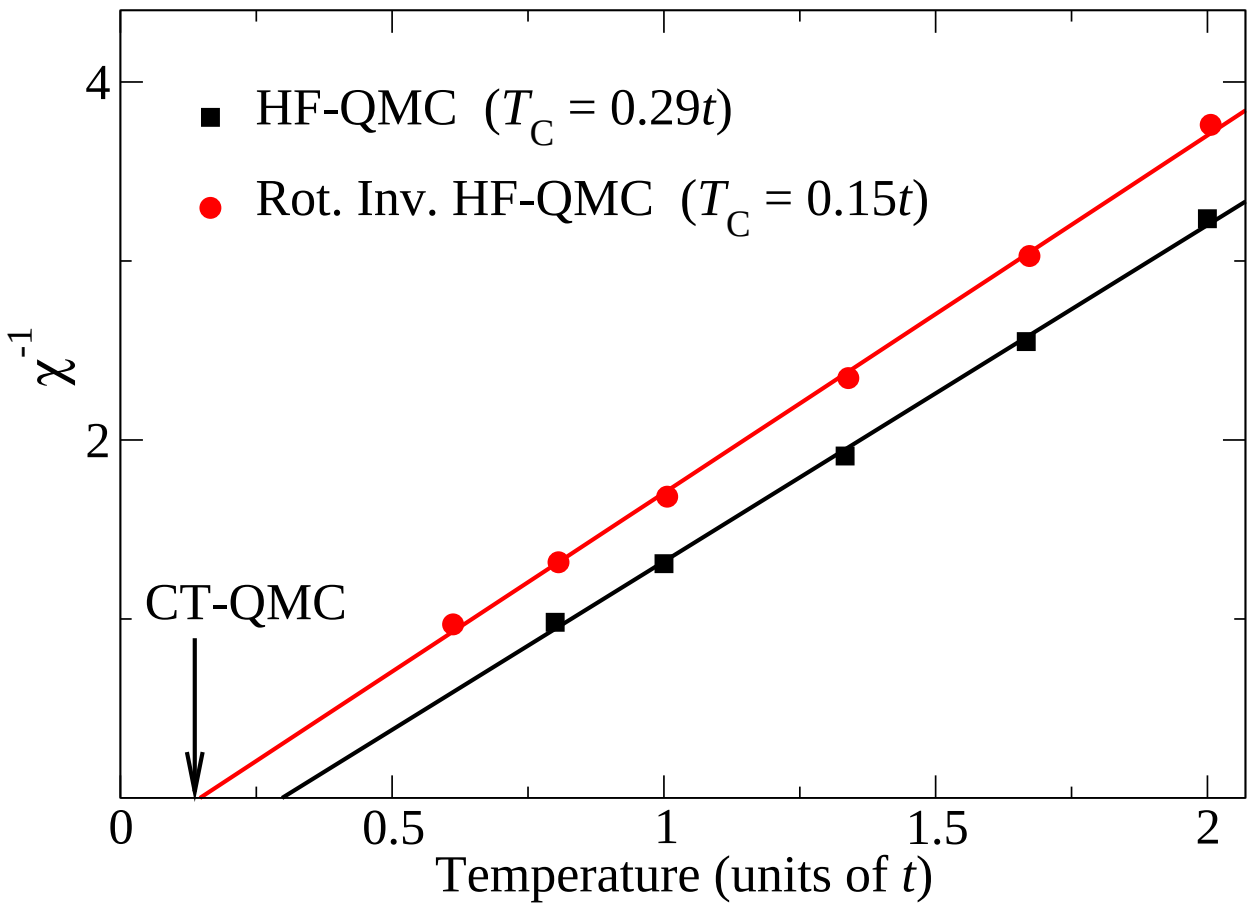

FIG. 1. (Color online) Temperature dependence of the inverse uniform magnetic susceptibility obtained by the DMFT for the three-band infinite-dimensional Bethe lattice. The parameters are chosen to be the same as in Fig. 3 of Ref. 10. The straight lines depict the least-squares fit to the Curie-Weiss law. The obtained Curie temperature values are $0.29t$ and $0.15t$ for HF-QMC and rotationally invariant HF-QMC, respectively. Our findings are in good quantitative agreement with results of the CT-QMC calculations presented in Ref. 10.

We now calculate the electronic structure and magnetic properties of paramagnetic bcc iron by employing the LDA+DMFT implemented with the rotationally invariant HF-QMC method. We first calculate the nonmagnetic LDA electronic structure of α iron using the tight-binding linear muffin-tin orbital (TB-LMTO) approach.[30] For these calculations we adopt lattice constant $a = 2.866$ Å. We construct an effective low-energy Hamiltonian in the basis of Fe *spd* Wannier orbitals using the Nth-order muffin-tin (NMTO) method.[31] In accord with the previous estimations,[7,24,25,32] we take $U = 2.3$ eV and $J = 0.9$ eV for the screened Coulomb interaction and Hund's exchange, respectively.

In Fig. 2 we present the partial density of states and the corresponding imaginary parts of the self-energies obtained by the rotationally invariant HF-QMC method at $T = 1160$ K in comparison with the non-magnetic LDA results. Our calculations reproduce the splitting in the density of states of the e_g orbitals near the Fermi level, which is absent in the LDA calculations. This result agrees well with the previous calculations[13,24,25] as well as with the experimental data and is one of the char-

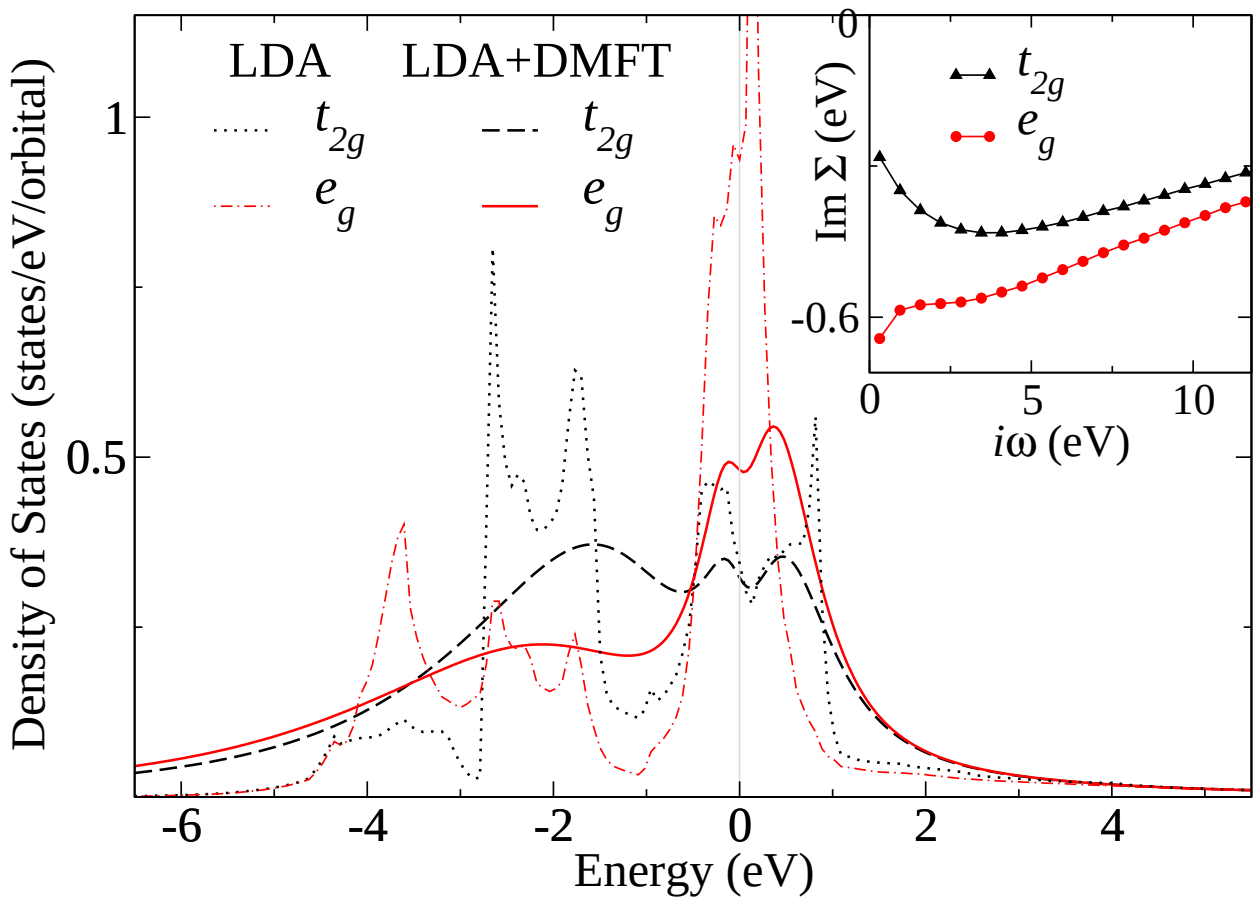

FIG. 2. (Color online) Partial t_{2g} (black) and e_g (red) densities of states for paramagnetic α iron as obtained by the rotationally invariant HF-QMC within LDA+DMFT in comparison with the non-magnetic LDA results. The Fermi level is indicated by the vertical (gray) line at zero energy. Inset: imaginary parts of the obtained self-energies.

acteristic features of α iron. The calculated self-energy for the t_{2g} states exhibits a Fermi-liquid-like behavior, whereas the e_g self-energy diverges at low frequencies. Our calculations with $J = 0$ recover the Fermi-liquid-like behavior for the e_g states resulting in the suppression of the splitting. This indicates that the splitting can be attributed to the exchange Coulomb interaction.[24] We found no evidence for the Hubbard subbands formation in the calculated quasiparticle spectrum. Thereby we conclude that in α iron the correlation effects are mainly effected by the strength of the Hund's coupling J rather than by the Coulomb interaction U which allow us to refer α iron as a Hund's metal. We note that importance of the Hund's exchange in multiorbital systems has been recently studied in Ref. 33.

The temperature dependence of the inverse uniform magnetic susceptibility calculated by the LDA+DMFT shows a linear behavior at high temperatures (Fig. 3) in accord with the Curie-Weiss law. It is clearly seen that the HF-QMC limited to the Ising-type exchange interaction substantially overestimates the Curie temperature value and yields $T_{\rm C} \sim 2050$ K. The rotationally invariant HF-QMC method gives $T_{\rm C} \sim 1260$ K, which is in good agreement with the experimental value of 1043 K (Ref. 29). The calculated values of effective local moments extracted from the uniform magnetic susceptibility are $\mu_{\rm eff} \sim 2.87\ \mu_{\rm B}$ and $2.61\ \mu_{\rm B}$ for the HF-QMC with density-density and rotationally invariant algorithms, respectively. Our estimates are in reasonable agreement with the experimental value of $3.13\ \mu_{\rm B}$ (Ref. 29), which appears to be underestimated by both methods.

We note that preserving the spin rotational symmetry turns out to be crucial for quantitative description of magnetic properties of correlated materials. In particular, for α iron this leads to substantial improvement of the magnetic transition temperature value. The remaining discrepancy can be attributed to non-local effects which are not present in conventional DMFT.

C. Nickel

Elemental nickel is another example of itinerant electron ferromagnets which together with iron serves as a benchmark material for electronic structure methods. Various low temperatures properties of nickel can be understood by employing standard band-structure approaches.[34] Nevertheless, these techniques are generally fail to reproduce many characteristic features of nickel, such as an existence of satellite structure[35] at -6 eV, $3d$ electron bandwidth,[36] and the value of exchange splitting.[36] Applications of LDA+DMFT to study the electronic and magnetic properties of nickel have given a good quantitative description of many of these phenomena.[7,25,27,28,37,38] The calculated magnetic properties of nickel are shown to be in good agreement with experiment. In contrast to iron, the overestimation of the magnetic transition temperature for nickel by LDA+DMFT with the Ising-type exchange interaction is not so significant.[7,39] However, as demonstrated below, preserving the spin rotational symmetry leads to the underestimation of the Curie temperature.

We now compute the electronic structure and magnetic properties of paramagnetic nickel by employing the LDA+DMFT implemented with rotationally invariant HF-QMC method. To obtain the non-magnetic LDA electronic structure of fcc nickel we employ the tight-binding linear muffin-tin orbital approach. The calculations were performed for the lattice constant $a = 3.524$ Å. Using these results we construct an effective low-energy

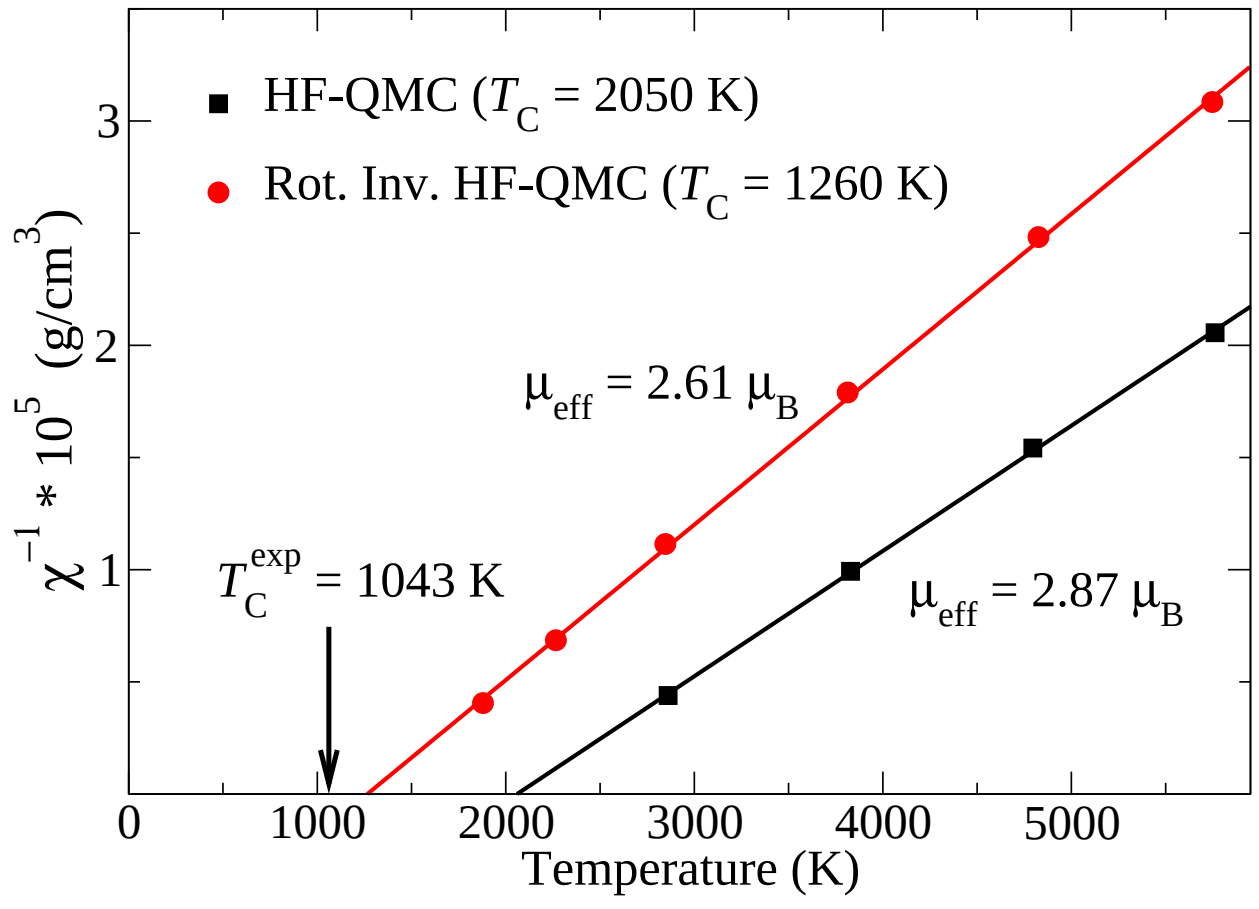

FIG. 3. (Color online) Temperature dependence of the inverse uniform magnetic susceptibility for α iron as obtained by the LDA+DMFT. The straight lines depict the least-squares fit to the Curie-Weiss law. The experimental value $T_{\rm C}^{\rm exp} = 1043$ K is denoted by the (black) arrow. The experimental value of the effective local magnetic moment is $\mu_{\rm eff}^{\rm exp} = 3.13\mu_B$ (Ref. 29).

Hamiltonian in the basis of Ni *spd* Wannier orbitals by employing the NMTO method. In accord with the previous estimations,[38] we take $U = 2.3$ eV and $J = 1.0$ eV for the screened Coulomb interaction and Hund's exchange, respectively.

In Fig. 4 we present the partial densities of states and the imaginary parts of the self-energies obtained by the rotationally invariant algorithm at $T = 1160$ K in comparison with the non-magnetic LDA results. The inclusion of electronic correlations results in a small reduction of the bandwidth of nickel with respect to the non-magnetic LDA result. In addition, a satellite-like structure emerges at about -5.5 eV. In contrast to iron, the obtained self-energies for both the t_{2g} and e_g orbitals exhibit the Fermi-liquid-like behavior. This can also be seen from the calculated amplitudes of the effective damping $\Im\Sigma(0)$ which are -0.03 eV and -0.02 eV for the t_{2g} and e_g states of nickel, respectively, while $\Im\Sigma(0) \sim -0.24$ eV for the t_{2g} states of α iron. This indicates more coherent nature of the electronic properties of nickel in comparison with iron. To quantify this qualitative difference[7,39] we calculate spin-spin correlation functions for iron and nickel. In Fig. 5 we present the impurity spin-spin correlation functions on the real and imaginary energy axes calculated for α iron and nickel at $T = 2.5\,T_{\mathrm{C}}$ (T_{C} refers here to the corresponding calculated value of the Curie temperature). The height of peak on the real energy axis can be interpreted as a value of the local magnetic moment. The pronounced peak for iron indicates the presence of well localized magnetic moments above T_{C}, while magnetism of nickel is more itinerant.

In Fig. 6 we show the temperature dependence of the inverse uniform magnetic susceptibility calculated by LDA+DMFT. From these data we estimate the values of the Curie temperature. By employing the density-density approximation we find $T_{\mathrm{C}} \sim 840$ K, whereas the inclusion of the spin rotational symmetry leads to almost twice smaller value of about 400 K. Both results are in reasonable agreement with the experimental value of 631 K. To proceed further, we compute the effective local magnetic moments by the HF-QMC and rotationally invariant methods which give $\mu_{\mathrm{eff}} \sim 1.55\ \mu_{\mathrm{B}}$ and $1.49\ \mu_{\mathrm{B}}$, respectively. These findings are in good agreement with the experimental value of $1.62\ \mu_B$ (Ref. 29). The fact that in α iron the LDA+DMFT with proper spin rotational symmetry results in an overestimated value of T_C, while it appears to be underestimated in nickel, can be dealt with non-local effects which are neglected in DMFT or with the more itinerant nature of magnetism in nickel than in α iron.

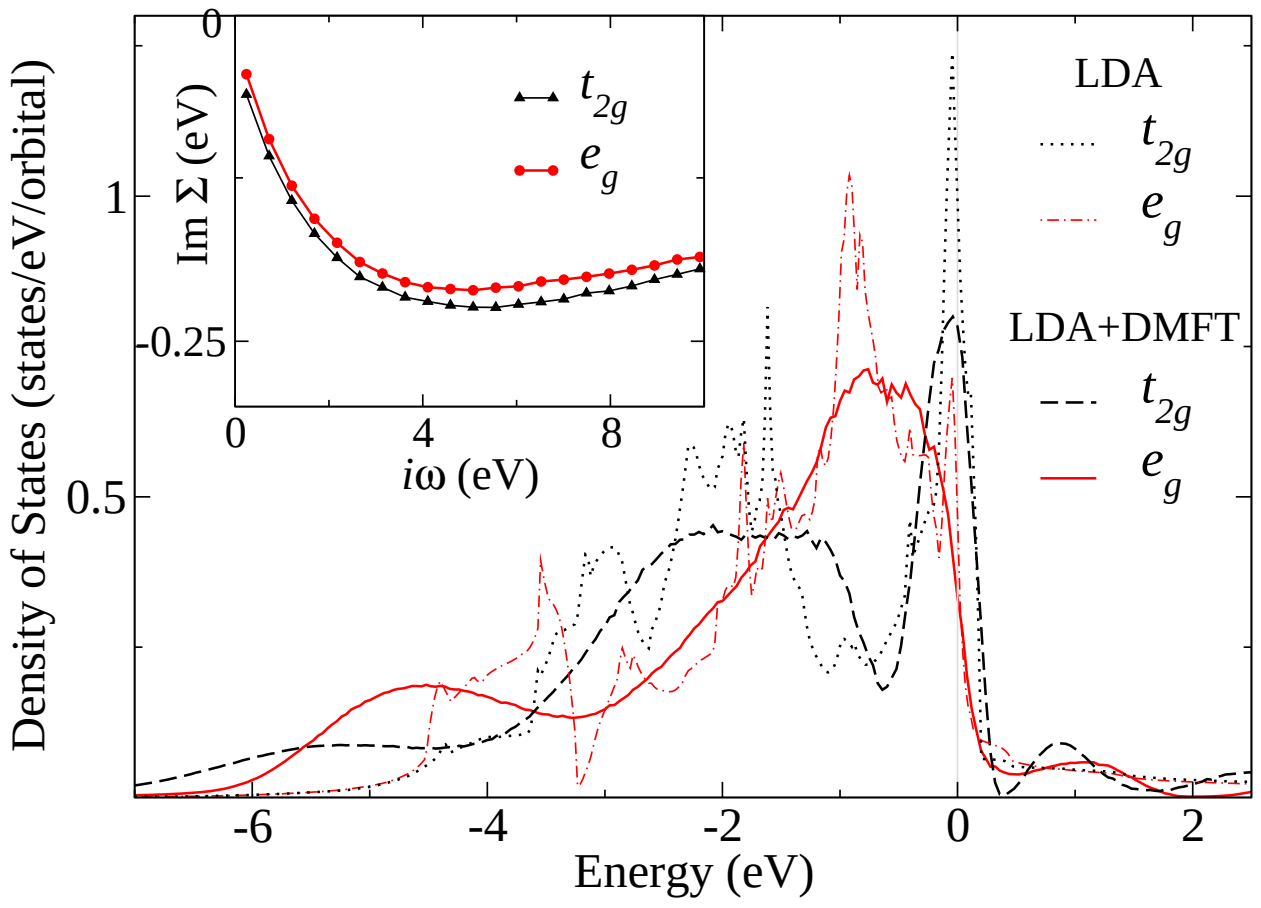

FIG. 4. (Color online) Partial densities of states for paramagnetic Ni obtained by rotationally invariant HF-QMC within LDA+DMFT in comparison with the LDA ones. The Fermi level is indicated by the vertical (gray) line at zero energy. Inset: imaginary parts of the obtained self-energies

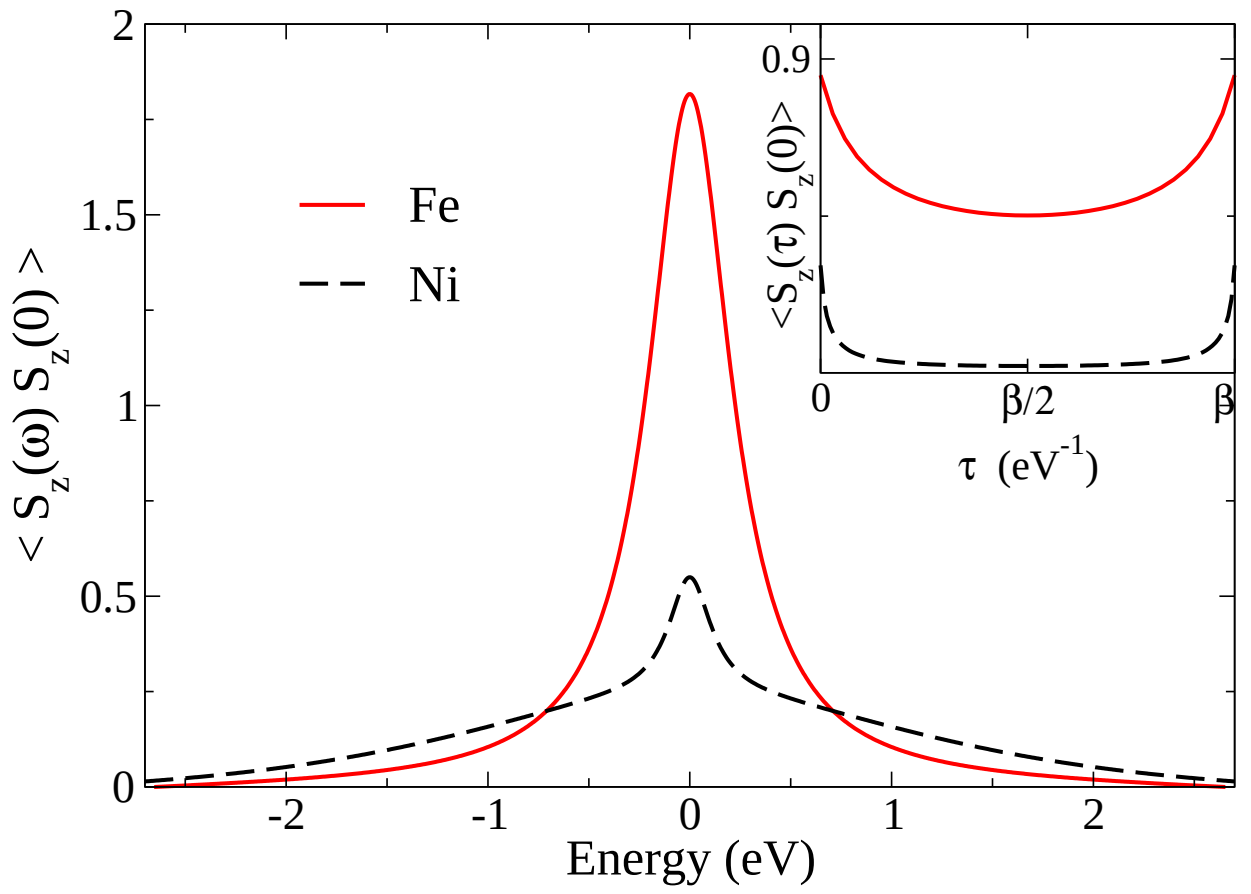

FIG. 5. (Color online) Spin-spin correlation functions on the real and imaginary (inset) energy axes for α iron and nickel calculated by LDA+DMFT at $T = 2.5\,T_{\mathrm{C}}$.

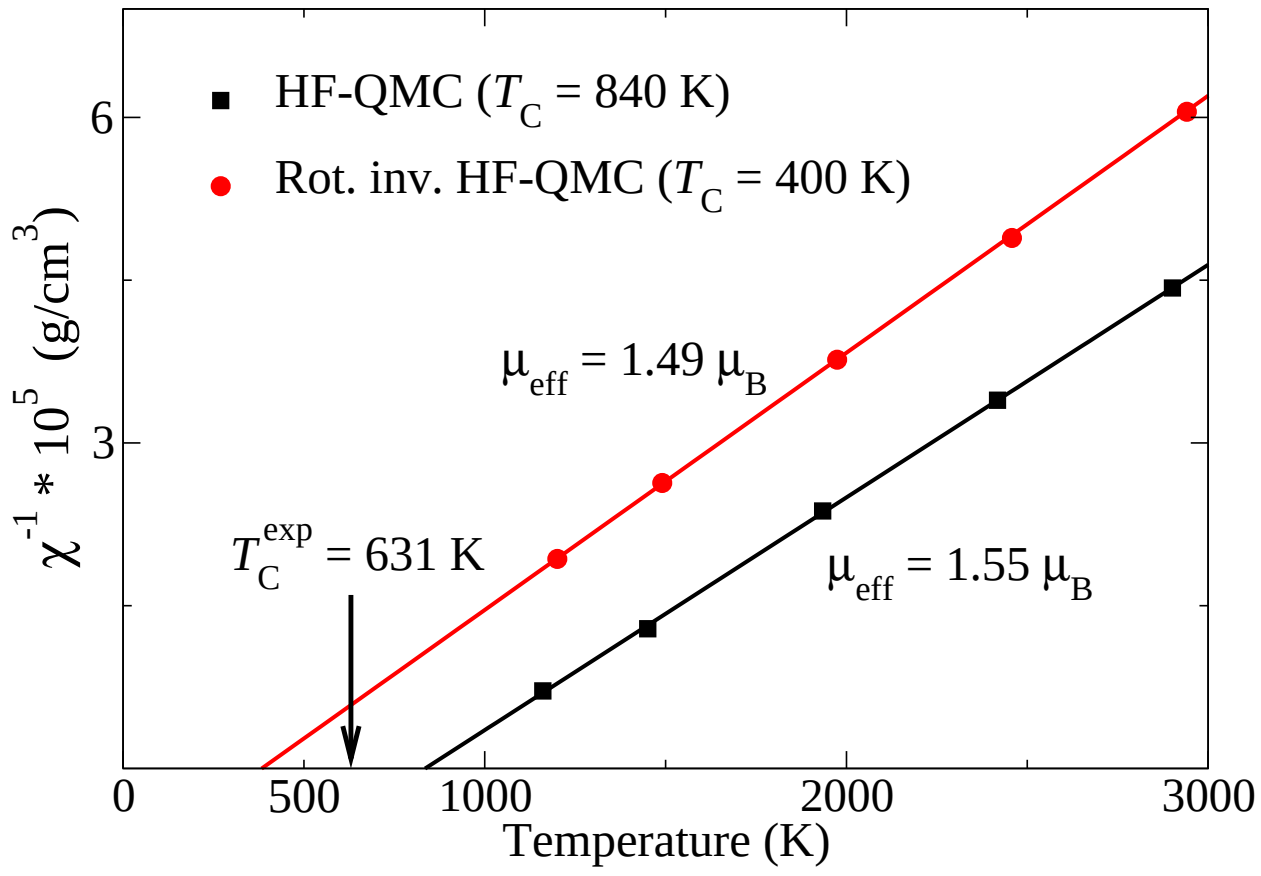

FIG. 6. (Color online) Temperature dependence of the inverse uniform magnetic susceptibility for Ni as obtained by LDA+DMFT. The straight lines depict the least-squares fit to the Curie-Weiss law. The experimental value $T_{\mathrm{C}}^{\mathrm{exp}} = 631$ K is denoted by the (black) arrow. The experimental value of the effective local magnetic moment is $\mu_{\mathrm{eff}}^{\mathrm{exp}} = 1.62\ \mu_B$ (Ref. 29).

IV. CONCLUSIONS

In conclusion, we have presented a novel implementation of the LDA+DMFT approach which allows one to take into account the spin rotational symmetry of the exchange Coulomb interaction. The computational scheme is based on extension of the Hirsch-Fye quantum Monte Carlo algorithm in which the spin rotational invariance of Hund's exchange is restored by averaging over all possible directions of spin quantization axis. The proposed approach provides a robust and computationally efficient method which allows us to compute high temperature electronic properties of the five-orbital systems. We have used this approach to perform benchmark calculations for the three-band Hubbard model on the infinite-dimensional Bethe lattice. Our results agree quantitatively well with those obtained using the continuous-time quantum Monte Carlo technique. The proposed method is employed to compute the electronic and magnetic properties of paramagnetic α iron and nickel. The obtained Curie temperatures agree well with experiment. Our results indicate that the density-density approximation for the exchange Coulomb interaction leads to substantial overestimation of the magnetic transition temperature. The remaining discrepancy in the calculated Curie temperatures can be attributed to non-local effects which are not taken into account in standard implementations of the LDA+DMFT.

ACKNOWLEDGMENTS

The authors thank A. Poteryaev for useful discussions. This work was supported by the Russian Foundation for Basic Research (Projects Nos. 10-02-00046a, 12-02-91371-CT_a, 12-02-31207), the grant of the Ministry of education and science of Russia 12.740.11.0026, the fund of the President of the Russian Federation for the support of scientific schools NSH-6172.2012.2, the Program of the Russian Academy of Science Presidium "Quantum microphysics of condensed matter". Support by the Deutsche Forschergemeinschaft through TRR 80 and FOR 1346 is gratefully acknowledged.

---

[1] W. Metzner and D. Vollhardt, Phys. Rev. Lett. **62**, 324 (1989); G. Kotliar and D. Vollhardt, Phys. Today **57**(3), 53 (2004); A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, Rev. Mod. Phys. **68**, 13 (1996).

[2] K. Held, I. A. Nekrasov, G. Keller, V. Eyert, N. Blümer, A. K. McMahan, R. T. Scalettar, Th. Pruschke, V. I. Anisimov, and D. Vollhardt, Phys. Status Solidi B **243**, 2599 (2006); K. Held, Adv. Phys. **56**, 829 (2007); V. Anisimov and Y. Izyumov, *Electronic Structure of Strongly Correlated Materials* (Springer, Berlin, 2010).

[3] M. Imada, A. Fujimori, and Y. Tokura, Rev. Mod. Phys. **70**, 1039 (1998).

[4] V. I. Anisimov, A. I. Poteryaev, M. A. Korotin, A. O. Anokhin, and G. Kotliar, J. Phys. Condens. Matter **9**, 7359 (1997); A. I. Lichtenstein and M. I. Katsnelson, Phys. Rev. B **57**, 6884 (1998).

[5] S. Biermann, A. Poteryaev, A. I. Lichtenstein, A. Georges, Phys. Rev. Lett. **94**, 026404 (2005); A. Kutepov, K. Haule, S. Y. Savrasov, and G. Kotliar, Phys. Rev. B **82**, 045105 (2010); B. Lazarovits, K. Kim, K. Haule, and G. Kotliar, *ibid.* **81**, 115117 (2010); A. S. Belozerov, M. A. Korotin, V. I. Anisimov, A. I. Poteryaev, *ibid.* **85**, 045109 (2012).

[6] A. I. Lichtenstein and M. I. Katsnelson, Phys. Rev. B **62**, R9283 (2000); G. Kotliar, S. Y. Savrasov, G. Palsson, and G. Biroli, Phys. Rev. Lett. **87**, 186401 (2001); P. Sun and G. Kotliar, Phys. Rev. B **66**, 085120 (2002); S. Biermann, F. Aryasetiawan, and A. Georges, Phys. Rev. Lett. **90**, 086402 (2003); M. Potthoff, M. Aichhorn, and C. Dahnken, *ibid.* **91**, 206402 (2003); A. Toschi, A. A. Katanin, and K. Held, Phys. Rev. B **75**, 045118 (2007); A. N. Rubtsov, M. I. Katsnelson, and A. I. Lichtenstein, *ibid.* **77**, 033101 (2008).

[7] A. I. Lichtenstein, M. I. Katsnelson, and G. Kotliar, Phys. Rev. Lett. **87**, 067205 (2001).

[8] I. Leonov, A. I. Poteryaev, V. I. Anisimov, and D. Vollhardt, Phys. Rev. Lett. **106**, 106405 (2011); I. Leonov, A. I. Poteryaev, V. I. Anisimov, and D. Vollhardt, Phys. Rev. B **85**, 020401(R) (2012).

[9] Th. Pruschke and R. Bulla, Eur. Phys. J. B **44**, 217 (2005).

[10] A. E. Antipov, I. S. Krivenko, V. I. Anisimov, A. I. Lichtenstein, and A. N. Rubtsov, Phys. Rev. B **86**, 155107 (2012).

[11] S. Sakai, R. Arita, K. Held, and H. Aoki, Phys. Rev. B **74**, 155102 (2006);

[12] A. E. Antipov, M. S. Aleinikov, and V. I. Anisimov, JETP Lett. **94**, 126 (2011).

[13] V. I. Anisimov, A. S. Belozerov, A. I. Poteryaev, I. Leonov, Phys. Rev. B **86**, 035152 (2012).

[14] R. Bulla, T. A. Costi, and T. Pruschke, Rev. Mod. Phys. **80**, 395 (2008).

[15] M. Caffarel and W. Krauth, Phys. Rev. Lett. **72**, 1545 (1994).

[16] A. N. Rubtsov, V. V. Savkin, and A. I. Lichtenstein, Phys. Rev. B **72**, 035122 (2005); P. Werner *et al.*, Phys. Rev. Lett. **97**, 076405 (2006); K. Haule, Phys. Rev. B **75**, 155113 (2007); A. M. Lauchli and P. Werner, *ibid.* **80**, 235117 (2009); E. Gull *et al.*, Rev. Mod. Phys. **83**, 349 (2011).

[17] J. Kunes, D. M. Korotin, M. A. Korotin, V. I. Anisimov, and P. Werner, Phys. Rev. Lett. **102**, 146402 (2009); A. S. Belozerov, A. I. Poteryaev, and V. I. Anisimov, JETP Lett. **93**, 73 (2011).

[18] E. Gorelov, T. O. Wehling, A. N. Rubtsov, M. I. Katsnelson, and A. I. Lichtenstein, Phys. Rev. B **80**, 155132 (2009); V. V. Mazurenko, S. N. Iskakov, A. N. Rudenko, V. I. Anisimov, and A. I. Lichtenstein, *ibid.* **82**, 193403 (2010); M. Aichhorn, S. Biermann, T. Miyake, A. Georges, and M. Imada, *ibid.* **82**, 064504 (2010); Z. P. Yin, K. Haule, and G. Kotliar, Nature Mat. **10**, 932 (2011); B. Surer, M. Troyer, P. Werner, T. O. Wehling, A. M. Lauchli,

A. Wilhelm, and A. I. Lichtenstein, Phys. Rev. B **85**, 085114 (2012).

[19] J. E. Hirsch and R. M. Fye, Phys. Rev. Lett. **56**, 2521 (1986).

[20] Strictly speaking, this parametrization of the Hamiltonian is appropriate for the two- and three-orbital systems. The five-band calculations require three effective Slater integrals ($F0$, $F2$, and $F4$) which can be linked to the U and J parameters.

[21] J. Hubbard, Phys. Rev. B **19**, 2626 (1979); *ibid.* **20**, 4584 (1979).

[22] P. Werner and A. J. Millis, Phys. Rev. Lett. **99**, 126405 (2007); P. Werner, E. Gull, M. Troyer, and A. J. Millis, *ibid.* **101**, 166405 (2008).

[23] S. Y. Savrasov, Phys. Rev. Lett. **81**, 2570 (1998); D. J. Singh, W. E. Pickett, and H. Krakauer, Phys. Rev. B **43**, 11628 (1991); L. Stixrude, R. E. Cohen, and D. J. Singh, *ibid.* **50**, 6442 (1994); A. Dal Corso and S. de Gironcoli, *ibid.* **62**, 273 (2000).

[24] A. A. Katanin, A. I. Poteryaev, A. V. Efremov, A. O. Shorikov, S. L. Skornyakov, M. A. Korotin, and V. I. Anisimov, Phys. Rev. B **81**, 045117 (2010).

[25] M. Katsnelson and A. Lichtenstein, J. Phys. Condens. Matter **11**, 1037 (1999).

[26] M. I. Katsnelson and A. I. Lichtenstein, Phys. Rev. B **61**, 8906 (2000).

[27] L. Chioncel, L. Vitos, I. A. Abrikosov, J. Kollar, M. I. Katsnelson, and A. I. Lichtenstein, Phys. Rev. B **67**, 235106 (2003).

[28] D. Benea, J. Minar, L. Chioncel, S. Mankovsky, and H. Ebert, Phys. Rev. B **85**, 085109 (2012).

[29] *Ferromagnetic Materials*, edited by E. P. Wolfarth (North-Holland, Amsterdam, 1986), Vol. 1.

[30] O. K. Andersen and O. Jepsen, Phys. Rev. Lett. **53**, 2571 (1984); O. K. Andersen, Z. Pawlowska, and O. Jepsen, Phys. Rev. B **34**, 5253 (1986).

[31] O. K. Andersen and T. Saha-Dasgupta, Phys. Rev. B **62**, 16219 (2000).

[32] M. Cococcioni and S. de Gironcoli, Phys. Rev. B **71**, 035105 (2005).

[33] L. de' Medici, J. Mravlje, and A. Georges, Phys. Rev. Lett. **107**, 256401 (2011).

[34] M. Cerny, J. Pokluda, M. Sob, M. Friak, and P. Sandera, Phys. Rev. B **67**, 035116 (2003).

[35] C. Guillot *et al.*, Phys. Rev. Lett. **39**, 1632 (1977).

[36] D. E. Eastman, F. J. Himpsel, and J. A. Knapp, Phys. Rev. Lett. **40**, 1514 (1978); F. J. Himpsel, J. A. Knapp, and D. E. Eastman, Phys. Rev. B **19**, 2919 (1979).

[37] J. Minar, L. Chioncel, A. Perlov, H. Ebert, M. I. Katsnelson, and A. I. Lichtenstein, Phys. Rev. B **72**, 045125 (2005); J. Braun, J. Minar, H. Ebert, M. I. Katsnelson, and A. I. Lichtenstein, Phys. Rev. Lett. **97**, 227601 (2006); I. Di Marco, J. Minar, S. Chadov, M. I. Katsnelson, H. Ebert, and A. I. Lichtenstein, Phys. Rev. B **79**, 115111 (2009); J. Minar, J. Phys. Condens. Matter **23**, 253201 (2011).

[38] M. I. Katsnelson and A. I. Lichtenstein, Eur. Phys. J. B **30**, 9 (2002).

[39] M. I. Katsnelson and A. I. Lichtenstein, J. Phys.: Condens. Matter **16**, 7439 (2004).